

S1 TOOL STEEL (60WCRV7)

S1 toolsteel is a cold work steel with very good toughness, is dimensionally stable, and impact resistant, with high hardening capacity. Applications: Cold shear knives, paper and wood cutting knives, cutting tools for plates up to 10 mm, ejector pins, air hammers.

Colour Code	Stocked Sizes		
	Rounds	20 mm - 150 mm Dia	
	Condition of Delivery		
	Soft annealed to max. 229 HB		

Related Specifications

Germany	DIN 1.2550
USA	AISI S1

Chemical Composition

	%
Carbon	0.60
Tungsten	2.00
Chromium	1.00
Vanadium	0.15

Physical Properties

Thermal expansion coefficient	$\left[\frac{10^{-6} \text{ m}}{\text{m K}} \right]$	<table><tr><th>20-100°C</th><th>20-200°C</th><th>20-300°C</th><th>20-400°C</th></tr><tr><td>10,9</td><td>11,5</td><td>12,0</td><td>12,4</td></tr></table>	20-100°C	20-200°C	20-300°C	20-400°C	10,9	11,5	12,0	12,4
20-100°C	20-200°C	20-300°C	20-400°C							
10,9	11,5	12,0	12,4							
Thermal conductivity	$\left[\frac{\text{W}}{\text{m K}} \right]$	<table><tr><th>20°C</th><th>350°C</th></tr><tr><td>31,9</td><td>29,6</td></tr></table>	20°C	350°C	31,9	29,6				
20°C	350°C									
31,9	29,6									

Heat Treatment

Soft Annealing

Temperature	740 - 760°C
Cooling	furnace
Hardness	max 229 HB


Stress Relief Annealing

Temperature	600 - 650°C
Cooling	furnace


Hardening

Temperature	860 - 900°C
Cooling	oil or hot bath 180 - 220°C
Hardness	see tempering diagram


Thermal Cycle Diagram

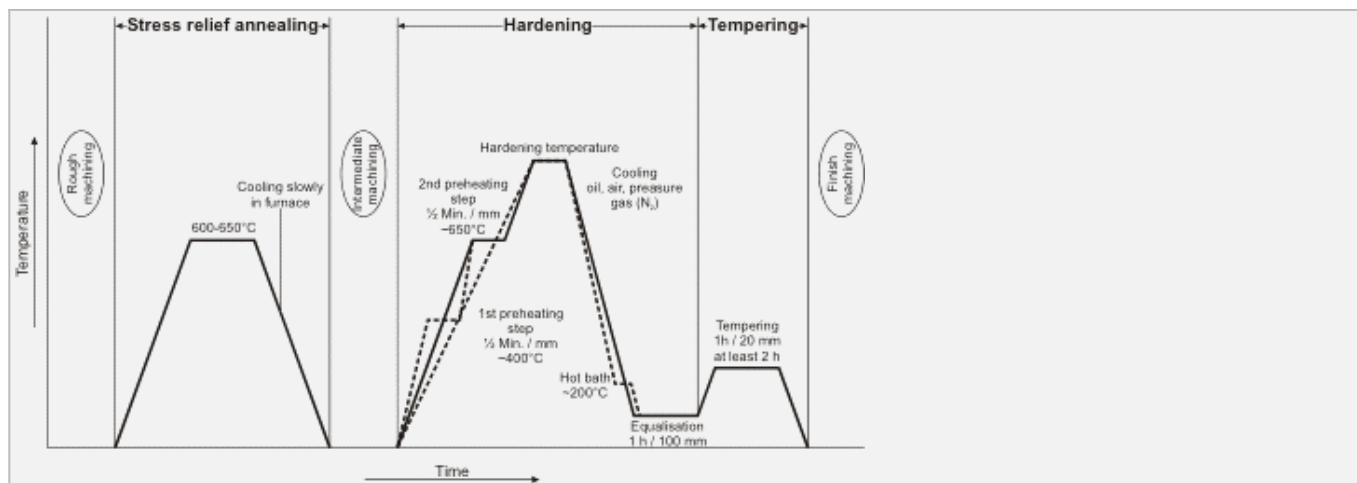

Continuous Cooling Transformation Diagram (CCT)

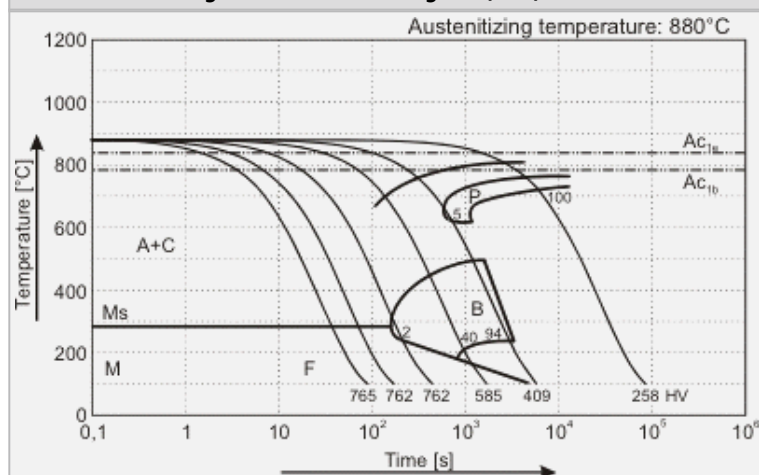

Tempering Diagram

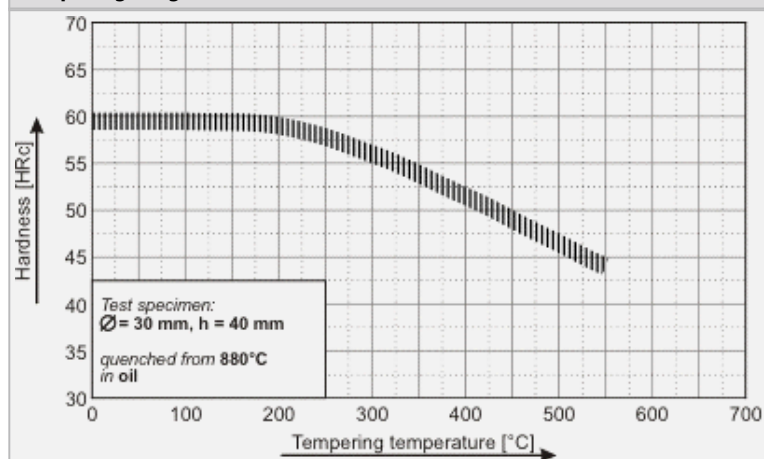

Interlloy believes the information provided is accurate and reliable. However no warranty of accuracy, completeness or reliability is given, nor will any responsibility be taken for errors or omissions.